

Fabrication of DNA Microarrays with Poly(L-glutamic acid) Monolayers on Gold Substrates for SPR Imaging Measurements

Yulin Chen, Anh Nguyen, Lifang Niu, and Robert M. Corn*

Department of Chemistry, University of California—Irvine, Irvine, California 92697

Received December 7, 2008. Revised Manuscript Received January 27, 2009

Robust single-stranded DNA (ssDNA) microarrays are created by attaching amine-modified oligonucleotides to a monolayer of poly(L-glutamic acid) (pGlu) that is electrostatically adsorbed onto a chemically modified gold thin film. This surface attachment chemistry methodology is first characterized with a combination of polarization-modulation Fourier transform infrared (PM-FTIR) spectroscopy and surface plasmon resonance (SPR) angle shift measurements. SPR imaging (SPRI) measurements of these ssDNA microarrays are then used to study two surface bioaffinity interactions: (i) the quantitative hybridization adsorption of complementary ssDNA onto mixed ssDNA microarray elements and (ii) the adsorption of single-stranded binding protein (SSB) onto fully and partially hybridized DNA microarray elements. The Langmuir adsorption coefficient (K_{Ads}) of SSB binding to ssDNA was determined to be $(5.5 \pm 0.4) \times 10^9 \text{ M}^{-1}$.

I. Introduction

DNA microarrays have become a mainstay for nucleic acid bioaffinity sensing measurements, with applications to a variety of biotechnological applications such as DNA diagnostics and detection,¹ gene expression analysis,² single nucleotide polymorphism (SNP) genotyping,³ and micro-RNA profiling.⁴ These arrays are used primarily for the detection and identification of cDNA or RNA by sequence-specific adsorption onto an array element consisting of single-stranded DNA (ssDNA) or RNA oligonucleotides that are chemically attached to the surface. It is assumed that the sequence specificity of the adsorption is due to the hybridization of the solution nucleic acids with the surface-bound oligonucleotides; this process is termed “hybridization adsorption”.

Although the vast majority of DNA microarray experiments detect the hybridization adsorption of fluorescently labeled DNA onto glass surfaces with fluorescence imaging, an increasingly popular alternative method is to detect the hybridization adsorption of unlabeled DNA or RNA onto chemically modified gold thin films with the optical technique of surface plasmon resonance imaging (SPRI).^{5,6} SPRI has been used to quantitatively detect not only unlabeled DNA and RNA but also the adsorption of unlabeled proteins such as transcription factors onto DNA microarrays.⁷ Recent SPRI biosensing applications of DNA microarrays are becoming increasingly complex, often augmenting a

hybridization adsorption event with a second surface enzymatic reaction to further process the adsorbed DNA and yield additional information.⁸ For example, SPRI measurements of SNP genotyping have been performed with DNA microarrays by using a surface ligation reaction after hybridization adsorption to detect and identify a single nucleotide in an adsorbed DNA strand.⁹

In all of these applications, it is essential to have a robust, noninterfering DNA attachment chemistry for the SPRI measurements on gold thin films. The microarray surface chemistry controls the accessibility and reactivity of the attached oligonucleotides for both hybridization adsorption and surface enzymatic processing. Moreover, the surface chemistry must control the specific and nonspecific adsorption of proteins and enzymes onto the array elements during the biosensing process. A variety of attachment chemistries on gold surfaces have been explored for the creation of “robust” DNA microarrays for SPRI; a common attachment strategy is the direct adsorption of a thiol-modified oligonucleotide onto the gold surface.^{10,11} While this method is important for electrochemical detection methods that require the DNA to be close to the metal–electrolyte interface, SPRI measurements can sense hybridization adsorption within 200 nm of the gold surface. Thus, attachment schemes that tether surface-bound “probe” oligonucleotides farther away from the surface can be used to obtain better hybridization adsorption performance. DNA microarrays on gold surfaces have also been created by attaching biotin-modified ssDNA to biotin-terminated alkanethiols via noncovalent biotin–streptavidin interactions.^{12,13} Surface attachment chemistries that use a protein such as streptavidin are potentially subject to additional nonspecific adsorption of proteins from solution via

*Corresponding author. E-mail: rcorn@uci.edu.

(1) Kimmel, A.; Oliver, B. *Methods in Enzymology: DNA Microarrays Part A: Array Platforms and Wet-Bench Protocols*; Academic Press: New York, 2006; Vol. 410.

(2) Schena, M.; Shalon, D.; Davis, R. W.; Brown, P. O. *Science* 1995, 270, 467–470.

(3) Fan, J. B.; Chen, X. Q.; Halushka, M. K.; Berno, A.; Huang, X. H.; Ryder, T.; Lipshutz, R. J.; Lockhart, D. J.; Chakravarti, A. *Genome Res.* 2000, 10, 853–860.

(4) Wark, A. W.; Lee, H. J.; Corn, R. M. *Angew. Chem., Int. Ed.* 2008, 47, 644–652.

(5) Nelson, B. P.; Grimsrud, T. E.; Liles, M. R.; Goodman, R. M.; Corn, R. M. *Anal. Chem.* 2001, 73, 1–7.

(6) Smith, E. A.; Corn, R. M. *Appl. Spectrosc.* 2003, 57, 320A–332A.

(7) Smith, E. A.; Erickson, M. G.; Ulijasz, A. T.; Weisblum, B.; Corn, R. M. *Langmuir* 2003, 19, 1486–1492.

(8) Lee, H. J.; Wark, A. W.; Corn, R. M. *Langmuir* 2006, 22, 5241–5250.

(9) Goodrich, T. T.; Lee, H. J.; Corn, R. M. *J. Am. Chem. Soc.* 2004, 126, 4086–4087.

(10) Herne, T. M.; Tarlov, M. J. *J. Am. Chem. Soc.* 1997, 119, 8916–8920.

(11) Peterlinz, K. A.; Georgiadis, R. M.; Herne, T. M.; Tarlov, M. J. *J. Am. Chem. Soc.* 1997, 119, 3401–3402.

(12) Zizlsperger, M.; Knoll, W. *Prog. Colloid Polym. Sci.* 1998, 109, 244–253.

(13) Shumaker-Parry, J. S.; Zareie, M. H.; Aebersold, R.; Campbell, C. T. *Anal. Chem.* 2004, 76, 918–929.

protein–protein interactions. Most “robust” DNA surface attachment chemistries create a covalent bond with the surface by reacting either an amine-modified ssDNA (at either the 5' or 3' end) to an amine-reactive surface monolayer to form an amide bond or a thiol-modified ssDNA to a thiol-reactive surface monolayer to form a sulfur–carbon or sulfur–sulfur bond. For the amine-reactive surface, a carboxylic acid-terminated alkanethiol is typically used to form an amide bond to the amine-modified ssDNA via a carbodiimide coupling reaction.^{14,15} Thiol-modified oligonucleotides have been attached to alkanethiol-modified gold surfaces via coupling reactions that form either a disulfide or a maleimide bond.^{16,17} For all of these attachment chemistries, it is essential that the surface coverage, bioavailability, and resistance to nonspecific adsorption of both DNA and proteins be thoroughly characterized.

In this paper, we characterize and implement a new methodology for ssDNA microarray fabrication that uses the chemical attachment of amine-modified oligonucleotides onto an electrostatically adsorbed monolayer of the anionic polypeptide poly(L-glutamic acid) (pGlu). SPR measurements demonstrate that these robust ssDNA microarrays exhibit very high surface hybridization efficiency, have very little nonspecific adsorption, provide additional biomolecule accessibility, and can be used in complex, multistep biosensing assays. The pGlu attachment chemistry process is depicted schematically in Figure 1. We have used pGlu monolayers previously in conjunction with monolayers of the cationic polypeptide poly(L-lysine) (pLys) to form ultrathin hydrophilic films at gold surfaces by the process of layer-by-layer (LbL) electrostatic adsorption.¹⁸ As shown in the figure, pGlu that is electrostatically adsorbed onto an amine-terminated alkanethiol monolayer is used to attach amine-modified DNA onto the gold film via a carbodiimide coupling reaction that simultaneously forms amide bonds between the pGlu and the amine-terminated DNA as well as the pGlu and the amine-terminated alkanethiol monolayer. This surface attachment chemistry differs from previous amine–carboxylic acid attachment chemistries that utilize an amide bond formation reaction with self-assembled monolayers or silane polymer films in several ways: (i) the use of electrostatic adsorption for pGlu deposition controls the amount and spacing of pGlu carboxylic acid groups on the surface, (ii) the amide bond formation reaction attaches both the amine-terminated ssDNA onto the pGlu and the pGlu onto the amine-terminated monolayer, and (iii) the use of pGlu provides additional flexibility for the surface-attached ssDNA, which makes it easier to hybridize and form dsDNA on the surface. A combination of polarization modulation Fourier transform infrared (PM-FTIR) spectroscopy and SPR angle shift measurements is used to characterize the formation of ssDNA monolayers on gold thin films. We then fabricate DNA microarrays and employ SPR to both quantitatively measure the hybridization adsorption of DNA onto the microarray elements and quantitatively monitor the adsorption

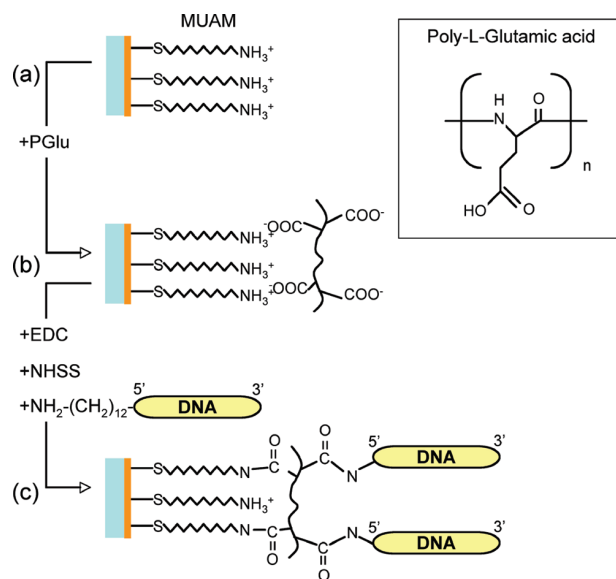


Figure 1. Three-step reaction scheme for attaching amine-terminated ssDNA onto gold surfaces. (a) A self-assembled monolayer of aminoundecanethiol (MUAM) is immobilized onto the gold substrate. (b) A monolayer of poly(L-glutamic acid) (pGlu) is electrostatically adsorbed onto the MUAM monolayer. (c) Amine-terminated ssDNA is covalently attached to the pGlu monolayer by a carbodiimide-catalyzed amide bond formation reaction using EDC and NHSS. At the same time, the pGlu monolayer is also covalently attached to the MUAM monolayer by the carbodiimide coupling reaction.

of single-stranded binding protein (SSB) onto fully and partially hybridized DNA microarrays. From these measurements, we calculate a Langmuir adsorption coefficient (K_{Ads}) of $(5.5 \pm 0.4) \times 10^9 \text{ M}^{-1}$.

II. Experimental Considerations

Materials. The chemicals 11-amino-1-undecanethiol hydrochloride (MUAM; Dojindo), poly(L-glutamic acid) sodium salt (MW = 50 000–100 000) (pGlu; Sigma), 1-ethyl-3-(3-(dimethylamino)propyl)carbodiimide hydrochloride (EDC; Pierce), *N*-hydroxysulfosuccinimide (NHSS; Pierce), and single-stranded DNA binding protein (MW = 75 372) (SSB; Epicenter Biotechnologies) were used as received.

A PBS buffer (100 mM Na_2HPO_4 , 0.3 M NaCl, 5 mM MgCl_2 , 1 mM EDTA, adjusted to pH 7.4) was used for all DNA and SSB binding measurements. Four ssDNA sequences were purchased from Integrated DNA Technologies and used as received; the sequences are denoted A, Ac, B, and Bc: A = 5'- $\text{NH}_2-(\text{CH}_2)_{12}$ -CGAAATCCAGACACATAAGCACGAA CCGAA-3'; Ac = 5'-TTCGGTTCGTGCTTATGTGTCTG GATTTTCG-3'; B = 5'- $\text{NH}_2-(\text{CH}_2)_{12}$ -(T)₃₀-3'; Bc = 5'-(A)₃₀-3'.

Two types of gold thin films were used in the experiments: (i) for SPR, 45 nm gold films with a 1 nm Cr underlayer were vapor-deposited onto SF10 glass slides (18 mm \times 18 mm, Schott Glass Technologies) using a Denton DV-502A evaporator, and (ii) for PM-FTIR, gold-coated silica slides (100 nm Au with a 5 nm Cr underlayer) were obtained from Evaporated Metal Films. All gold films were rinsed with ethanol and water prior to use.

DNA Attachment Chemistry. ssDNA was attached onto the gold films in a three-step process: (i) formation of a self-assembled MUAM monolayer by immersion of the slide in a 1 mM ethanolic MUAM solution for at least 24 h; (ii) pGlu monolayer formation by immersion in 2 mg/mL pGlu solution in PBS buffer for 1 h; (iii) exposure of the surface to an optimized

(14) Phillips, K. S.; Han, J. H.; Martinez, M.; Wang, Z. Z.; Carter, D.; Cheng, Q. *Anal. Chem.* **2006**, *78*, 596–603.

(15) Strother, T.; Knickerbocker, T.; Russell, J. N.; Butler, J. E.; Smith, L. M.; Hamers, R. J. *Langmuir* **2002**, *18*, 968–971.

(16) Smith, E.; Wanat, M. J.; Cheng, Y.; Barreira, S. V. P.; Frutos, A. G.; Corn, R. M. *Langmuir* **2001**, *17*, 2502–2507.

(17) Brockman, J. M.; Frutos, A. G.; Corn, R. M. *J. Am. Chem. Soc.* **1999**, *121*, 8044–8051.

(18) Frutos, A. G.; Weibel, S. C.; Corn, R. M. *Anal. Chem.* **1999**, *71*, 3935–3940.

250 μM amine-modified ssDNA solution in a PBS buffer that contained 75 mM EDC and 15 mM NHSS for 4 h. Each step was followed by a rinsing step and drying in a nitrogen stream. The first rinsing step used ethanol followed by water. The second and third rinsing steps used water.

DNA Microarray Fabrication. ssDNA microarrays were fabricated using a metal mask to vapor deposit 12 gold film spots (1.0 mm diameter) onto SF10 glass slides. Amine-terminated ssDNA (sequences A and B in different percentage ratios) was attached to the gold array spots with the DNA surface attachment chemistry described above; 0.5 μL of a 250 μM amine-terminated ssDNA solution was used for each spot. Control spots were created by exposure of the gold surface to only MUAM and then pGlu. The microarray was rinsed with water and dried by nitrogen gas prior to use. For the hybridization adsorption experiments, 500 μL of a 1 μM complementary ssDNA solution (sequences Ac or Bc) was introduced into the in-situ SPRI cell and allowed to react for 15 min. For the SSB binding experiments, 500 μL of a 10 nM SSB solution was introduced into the in-situ SPRI cell and allowed to react for 15 min.

PM-FTIR Measurements. PM-FTIR spectra were obtained using a Mattson RS-1 spectrometer with real-time interferogram sampling electronics and an optical layout described previously.¹⁹ Spectra in the mid-IR region (1000–2000 cm^{-1}) were collected by coadding 1000 scans at 4 cm^{-1} resolution. The PM-FTIR differential reflectance ($\%\Delta R$) values were converted to absorbance units as described elsewhere.¹⁹

Scanning Angle SPR Measurements. A scanning angle SPR apparatus (percent reflectivity ($\%R$) vs incident angle (θ)) was constructed using the following components: a 632.8 nm HeNe laser (JDS Uniphase, 7.5 mW), a polarizer, a mechanical chopper (Stanford Research System, SR540, 1000 Hz), a stepper motor-controlled θ – 2θ rotating angle stage with 0.0025° resolution, a photodiode detector (EG&G), and a lock-in amplifier (EG&G, 7220 DSP). The instrument was controlled by computer using a LabVIEW program (National Instruments). The samples were placed on the rotating stage in an in-situ cell consisting of a 60° SF10 prism and a 100 μL flow cell described elsewhere.²⁰ The p-polarized reflectivity data were converted to $\%R$ by setting the value of the reflectivity at the critical angle equal to 85% and are plotted as $\%R$ vs θ .

SPR Imaging Measurements. SPRI measurements of differential reflectivity images ($\Delta\%R$) at 830 nm were obtained using an SPRImager instrument (GWC Technologies) as described elsewhere.²¹

III. Results and Discussion

A. PM-FTIR and SPR Angle Shift Characterization Measurements. A combination of PM-FTIR spectroscopy and SPR angle shift measurements was used to characterize the attachment chemistry for immobilizing ssDNA onto chemically modified gold thin films, as shown in Figure 1. The DNA attachment chemistry is composed of three steps: (i) formation of an amine-terminated alkanethiol self-assembled monolayer of MUAM on the gold thin film, (ii) the electrostatic adsorption of a monolayer of pGlu onto the positively charged MUAM monolayer, and (iii) the creation of a DNA monolayer by the simultaneous covalent attachment via an EDC/NHSS carbodiimide coupling reaction of the pGlu carboxylic acid moieties with the MUAM

monolayer and the amine-terminated ssDNA oligonucleotides from solution. The use of a pGlu monolayer provides additional freedom for the amide bond formation reaction and increases the ssDNA availability for hybridization and protein binding.

PM-FTIR Measurements. The PM-FTIR spectra of the ssDNA monolayer attachment chemistry are shown in Figure 2. The mid-IR region of the PM-FTIR spectrum of the MUAM alkanethiol monolayer is shown in the figure as trace (a). This spectrum is featureless except for a small CH_2 bending/rocking band at 1461 cm^{-1} . After exposing the MUAM monolayer to a pGlu solution, the spectrum labeled (b) in Figure 2 is obtained. This PM-FTIR spectrum shows several new bands due to the electrostatic adsorption of pGlu onto the surface: the characteristic amide I and amide II bands of the polypeptide backbone at 1660 and 1542 cm^{-1} , respectively, and bands at 1720 and 1400 cm^{-1} (very weak) which are assigned respectively to the protonated carboxylic acid groups $\text{R}-\text{COOH}$ and the carboxylate groups $\text{R}-\text{COO}^-$ of the pGlu monolayer. The presence of a protonated carboxylic acid band in the spectrum suggests that not all of the carboxylic acids in the pGlu can interact with the $\text{R}-\text{NH}_3^+$ groups of the MUAM monolayer. For comparison, the PM-FTIR spectrum of an electrostatic multilayer film formed by the alternating deposition of pGlu and poly(L-lysine) (pLys) shows a very strong carboxylate band at 1400 cm^{-1} .²² The electrostatic nature of the pGlu adsorption onto the MUAM monolayer was verified by loss of the amide I and amide II bands from the surface PM-FTIR spectrum when the slides were rinsed with either a low-pH solution (2 M HCl, pH = 2) or high-pH solution (2 M NaOH, pH = 11). At these pH values the formation of either $\text{R}-\text{COOH}$ or $\text{R}-\text{NH}_2$ leads to the disruption of the $\text{NH}_3^+/\text{COO}^-$ electrostatic interactions and desorption of the pGlu monolayer.

Oligonucleotides were chemically attached to the pGlu monolayer by exposing the surface to a solution of amine-terminated ssDNA that contained the coupling reagents EDC and NHSS. The EDC and NHSS simultaneously catalyze two amide bond formation reactions with the pGlu carboxylic acid side chains: the attachment of amine-terminated ssDNA to the pGlu monolayer and the attachment of pGlu monolayer to the MUAM monolayer. The PM-FTIR spectrum of the monolayer after these reactions is shown in Figure 2 as curve c. The $\text{R}-\text{COOH}$ band at 1720 cm^{-1} has disappeared, and two new bands at 1255 and 1106 cm^{-1} have appeared and are assigned to phosphate group vibrations from the ssDNA that has been attached onto the surface. The intensity of these bands is comparable to those observed from ssDNA monolayers attached to gold surfaces with other reaction schemes.^{16,23} From a phosphate band absorbance of 5×10^{-4} AU at 1106 cm^{-1} , we can estimate a ssDNA surface density of $(4 \pm 2) \times 10^{12}$ molecules/ cm^2 .²⁴

SPR Angle Shift Measurements. To complement the PM-FTIR monolayer characterization experiments, a set of sequential SPR angle shift measurements were used to evaluate film thickness during the surface attachment chemistry. Figure 3 shows a set of four SPR reflectivity curves obtained in PBS buffer. The first curve (dashed line) was obtained from the bare gold surface, and the second curve

(19) Frey, B. L.; Corn, R. M.; Weibel, S. C. *Handbook of Vibrational Spectroscopy*; John Wiley & Sons: Chichester, 2001; Vol. 2.

(20) Goodrich, T. T.; Wark, A. W.; Corn, R. M.; Lee, H. J. *Methods in Molecular Biology*; Humana Press: New York, 2006; Vol. 328.

(21) Lee, H. J.; Nedelkov, D.; Corn, R. M. *Anal. Chem.* 2006, 78, 6504–6510.

(22) Cheng, Y. F.; Corn, R. M. *J. Phys. Chem. B* 1999, 103, 8726–8731.

(23) Jordan, C. E.; Frutos, A. G.; Thiel, A. J.; Corn, R. M. *Anal. Chem.* 1997, 69, 4939–4947.

(24) Lee, H. J.; Li, Y.; Wark, A. W.; Corn, R. M. *Anal. Chem.* 2005, 77, 5096–5100.

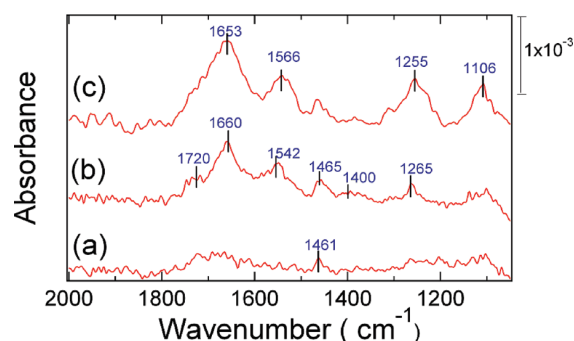


Figure 2. PM-FTIR spectra of the three-step ssDNA surface attachment chemistry: (a) self-assembled MUAM monolayer; (b) addition of an electrostatically adsorbed pGlu monolayer; (c) addition of covalently attached ssDNA to the pGlu monolayer. FTIR band assignments are listed in Table 1.

Table 1. PM-FTIR Assignments for the MUAM–pGlu Monolayer

| surface | wavenumber (cm ⁻¹) | assignment | Figure |
|---------|--------------------------------|--------------------------------------|--------|
| MUAM | 1461 | CH ₂ scissors deformation | 2a |
| pGlu | 1265 | CH ₂ bending | 2b |
| | 1400 | COO ⁻ | 2b |
| | 1660 | amide I | 2b |
| | 1542 | amide II | 2b |
| | 1720 | COOH | 2b |
| ssDNA | 1106, 1255 | phosphate band | 2c |

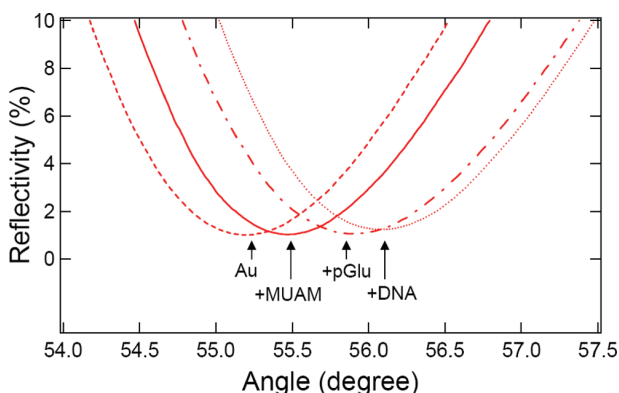


Figure 3. In-situ scanning SPR curves (reflectivity vs incident angle) of the three-step DNA attachment chemistry onto a 45 nm gold thin film. The four SPR curves are obtained from bare gold (dashed line), after the formation of a self-assembled MUAM monolayer (solid line), after the electrostatic adsorption of a pGlu monolayer (dash-dotted line), and after the attachment of amine-terminated ssDNA (dotted line). See Table 2 for the SPR angle shifts and film thicknesses.

(solid line) was obtained after the formation of a MUAM monolayer on the gold thin film. A shift of 0.26° of the SPR angle was observed (as listed in Table 2). Utilizing a four-phase Fresnel calculation program^{25–27} (SF10/gold/MUAM/buffer) employing the refractive indices listed in Table 2, we calculated a MUAM monolayer thickness of 1.8 nm. This value is in agreement with other SPR

Table 2. SPR Angle Shifts and Calculated Film Thicknesses

| | $\Delta\theta$ (deg) | refractive index | no. of phases | effective thickness (nm) |
|---------|----------------------|--------------------|---------------|--------------------------|
| MUAM | 0.26 ± 0.01 | 1.45 ²⁵ | 4 | 1.80 ± 0.03 |
| + pGlu | 0.43 | 1.52 ²⁸ | 5 | 1.72 |
| + ssDNA | 0.19 | 1.41 ³⁶ | 6 | 1.07 |

C₁₁ alkanethiol monolayer thickness measurements.²³ The third curve in Figure 3 (dash-dotted line) was obtained after the electrostatic adsorption of a pGlu monolayer. An additional SPR angle shift of 0.43° was observed, and a pGlu monolayer thickness of 1.7 nm was obtained from a five-phase Fresnel calculation (SF10/gold/MUAM/pGlu/buffer). This thickness is similar to that calculated from other SPR measurements of electrostatically adsorbed pGlu monolayers.^{25,28} The fourth curve (dotted line) in Figure 3 was obtained after the amide attachment reaction of the ssDNA to the surface. An additional shift of 0.19° was observed. A six-phase Fresnel calculation (SF10/gold/MUAM/pGlu/ssDNA/buffer) was used to determine a ssDNA monolayer thickness of 1.1 nm. This value is similar to that obtained previously from SPR measurements on ssDNA monolayers attached onto pLys-modified gold thin films.²³ From this series of SPR angle shift measurements, we can confirm that (i) the reaction scheme in Figure 1 reliably leads to the formation of a 1.1 nm ssDNA monolayer and (ii) this ssDNA monolayer is spaced from the gold surface by an ultrathin (1.7 nm) pGlu monolayer for increased bioavailability.

B. SPRI Measurements of Hybridization Adsorption. Having characterized the pGlu ssDNA attachment chemistry, a set of SPRI measurements were performed to determine the fidelity of DNA hybridization adsorption onto these ssDNA monolayers. Quantitative SPRI measurements of DNA hybridization adsorption were performed on a six-element DNA microarray; the six ssDNA elements were created by spotting solutions containing mixtures of two amine-terminated 30mer oligonucleotides A and B (sequences for A and B are listed in the II Experimental Considerations) with an A:B percentage of 100:0, 80:20, 60:40, 40:60, 20:80, and 0:100. Sequences A and B were checked using mfold RNA/DNA folding calculations (developed by M. Zuker)²⁹ to avoid any hairpin formation. It is reasonable to assume that the two amine-terminated ssDNA sequences have equivalent surface reactivity, so that the A:B percentage of the surface bound ssDNA should be the same as in solution. Figure 4a shows the arrangement of the ssDNA array elements used in the SPRI experiments, and Figures 4b and 4c show the SPR images obtained after exposing the array to a 1 μ M solution of either the 30mer complement of A (denoted Ac) or the 30mer complement of B (denoted Bc), respectively. The sequences for Ac and Bc are listed in the II Experimental Considerations. Previous measurements have shown that the surface coverage of adsorbed complementary ssDNA is directly proportional to the SPR reflectivity increase ($\Delta\%R$) when $\Delta\%R$ is less than 10%.³⁰ In addition, the Langmuir adsorption coefficient for DNA hybridization adsorption has

(25) Frey, B. L.; Jordan, C. E.; Kornguth, S.; Corn, R. M. *Anal. Chem.* **1995**, *67*, 4452–4457.

(26) Hansen, W. N. *J. Opt. Soc. Am.* **1968**, *58*, 380–388.

(27) Jordan, C. E.; Frey, B. L.; Kornguth, S.; Corn, R. M. *Langmuir* **1994**, *10*, 3642–3648.

(28) Frutos, A. G.; Weibel, S. C.; Corn, R. M. *Anal. Chem.* **1999**, *71*, 3935–3940.

(29) Zuker, M. *Nucleic Acids Res.* **2003**, *31*, 3406–3415.

(30) Nelson, B. P.; Grimsrud, T. E.; Liles, M. R.; Goodman, R. M.; Corn, R. M. *Anal. Chem.* **2001**, *73*, 1–7.

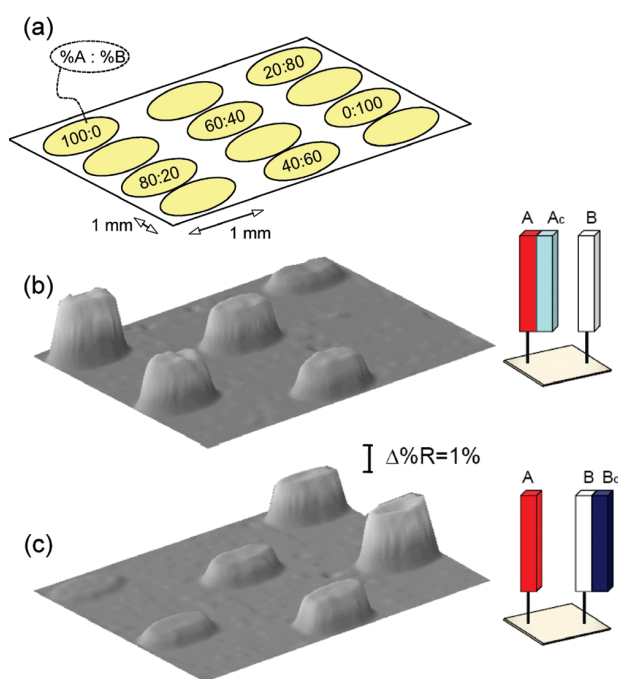


Figure 4. SPRI measurements of DNA hybridization adsorption onto an ssDNA microarray containing mixtures of two 30mer sequences (A and B). (a) The arrangement of the six ssDNA microarray elements for the SPRI experiments. Each element contained the sequences A and B in a different percentage ratio denoted as %A:%B. (b) SPRI difference image obtained after the hybridization adsorption of the ssDNA complement Ac onto the microarray from a $1\ \mu\text{M}$ solution. (c) SPRI difference image obtained after the hybridization adsorption of the ssDNA complement Bc onto the microarray from a $1\ \mu\text{M}$ solution.

a previously measured value of $1.8 \times 10^7\ \text{M}^{-1}$,³⁰ so that at a bulk target ssDNA concentration of $1\ \mu\text{M}$ there should be a full monolayer of dsDNA on the surface. Quantitative results of $\Delta\%R$ as a function of %A and %B obtained from those two images are plotted, as shown in Figure 5. There are three important points that can be ascertained from the data in this figure:

First, the SPRI reflectivity changes for both the 100% A monolayer exposed to Ac and the 100% B monolayer exposed to Bc was $\Delta\%R = 2.4 \pm 0.3\%$. Using SPRI measurements of $\Delta\%R$ obtained in previous DNA hybridization adsorption experiments, we can estimate a total adsorbed complementary ssDNA surface density of roughly 4×10^{12} molecules/ cm^2 .³¹ This estimate of surface density is the same value that we obtained from the PM-FTIR measurements for the surface density of the ssDNA attached to the pGlu monolayer. These results suggest that the surface hybridization efficiency of this surface is very high, approaching 100%. As mentioned above, a high surface hybridization efficiency is reasonable given that these hybridization adsorption measurements were performed at a complementary ssDNA concentration of $1.0\ \mu\text{M}$, which corresponds to a full monolayer given a Langmuir adsorption coefficient of $1.8 \times 10^7\ \text{M}^{-1}$.⁵

A second point is that the SPRI signal for both the 100% A monolayer exposed to Bc and the 100% B monolayer exposed to Ac is $\Delta\%R = 0.0 \pm 0.3\%$. This demonstrates that there is no nonspecific adsorption of noncomplementary

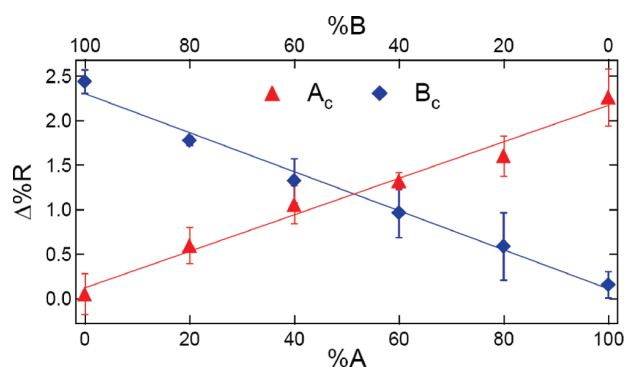


Figure 5. Quantitative plot of SPR reflectivity difference ($\Delta\%R$) vs A:B percentage (%A or %B) for the DNA hybridization adsorption measurements. The $\Delta\%R$ values are obtained from the SPRI difference images in Figure 4: triangles are from the Ac adsorption experiment (Figure 4b), and diamonds are from the Bc adsorption experiment (Figure 4c). The error bars represent the standard deviations obtained from three separate experiments.

oligonucleotides onto the ssDNA monolayer; only binding to the complementary sequence is observed. This sequence specificity of DNA adsorption is the primary evidence that the adsorption process includes DNA hybridization.

Third, the two lines in Figure 5 from 0% A to 100% A and 0% B to 100% B are straight and intersect at $\sim 50\%$. This demonstrates that (i) the amine attachment chemistry has the same reaction efficiency for the two sequences and (ii) the amount of hybridization adsorption is the same for the two sequences. Moreover, since the amount of hybridization is linear with the fraction of the surface that is ssDNA, there are no crowding or electrostatic effects (which would lead to nonlinear Frumkin-like terms in the adsorption isotherm) that would limit the amount of DNA adsorption onto these monolayers. The absence of electrostatic limitations on DNA hybridization adsorption also implies a very high DNA surface hybridization efficiency on the surface; a more precise demonstration of this will be seen in the subsequent SSB binding measurements.

In these SPRI experiments, the smallest amount of dsDNA formed from hybridization adsorption that can be detected on the surface is a relative surface coverage (θ) of 5%. This corresponds to a limit of detection for target DNA concentration in solution (C_{LOD}) of 2.5 nM as determined from the following equation: $C_{\text{LOD}} = \theta/K_{\text{Ads}} = 0.05/(1.8 \times 10^7)$. This C_{LOD} is similar to the value determined in a previous paper using maleimide-attached ssDNA monolayers.³⁰ All of these findings indicate that the pGlu attachment chemistry affords ample space and flexibility for the DNA strands on the surface to interact with molecules in solution and not interact with each other.

C. SPRI Imaging Measurements of SSB Adsorption onto DNA Microarrays. Having confirmed that the pGlu ssDNA attachment chemistry can be used to create ssDNA monolayers that are well-behaved with respect to the hybridization adsorption of DNA, the next question is: can these surfaces be used to study protein–DNA interactions? To answer this question, a series of SPRI experiments were performed to study the adsorption of SSB to the mixed sequence DNA monolayers. SSB is a 75 kDa tetrameric protein that binds to ssDNA sequences, but not dsDNA.³²

(31) Li, Y.; Lee, H. J.; Corn, R. M. *Nucleic Acids Res.* **2006**, *34*, 6416–6424.

(32) Meyer, R. R.; Laine, P. S. *Microbiol. Rev.* **1990**, *54*, 342–380.

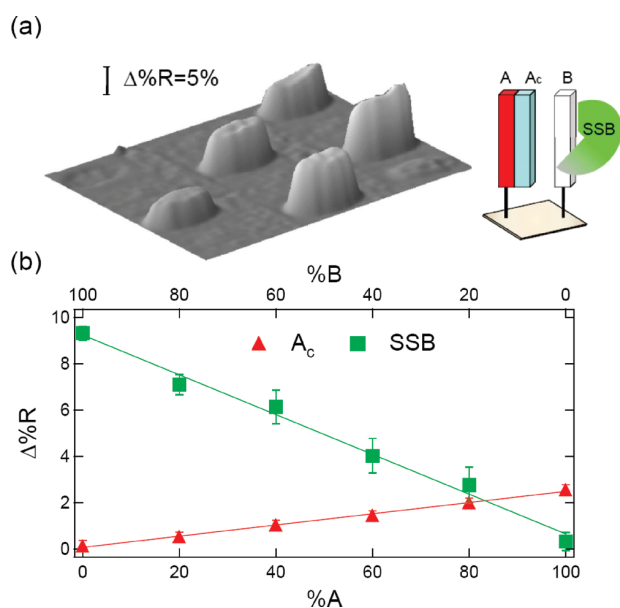


Figure 6. SPRI measurements of single-stranded binding protein (SSB) adsorption onto a partially hybridized ssDNA microarray containing mixtures of dsDNA (A-Ac) and ssDNA (B). The %A:%B ratios are the same as in Figure 4a. The microarray is first exposed to a 1 μ M solution of the complement Ac and then to a 10 nM solution of SSB. (a) SPR difference image of the microarray after SSB adsorption. (b) Quantitative plot of $\Delta\%R$ vs A:B percentage for the initial hybridization adsorption of Ac (triangles) and the subsequent adsorption of SSB (squares).

To demonstrate the preferential affinity of SSB to ssDNA and not dsDNA, SPRI measurements were performed onto the DNA microarrays that we created in section IIIB. The microarrays were sequentially exposed to complementary ssDNA and then SSB. Figure 6a is the SPR image of an array that was first exposed to the complement Ac and then to a 10 nM solution SSB. Figure 6b plots the quantitative results obtained from the SPRI measurements. Figures 7a and 7b are the similar SPR image and data for an array that was first exposed to the complement Bc and then SSB. The SPRI signal due to SSB adsorption is ~ 5 times larger ($\Delta\%R \approx 10\%$) than the SPR signal observed from cDNA hybridization adsorption ($\Delta\%R \approx 2\%$). This large signal is primarily due to the larger molecular weight (~ 75 kDa) of the SSB as comparing to Ac or Bc (~ 10 kDa).

As the percentage of ssDNA on the surface is reduced due to hybridization adsorption, the SPR signal due to SSB adsorption also decreases. From the linear plots in Figures 6b and 7b, it is clear that the SSB binds specifically with ssDNA (and not dsDNA). This observation is in agreement with the finding from other SSB studies.³³ In addition, the SPRI measurements show that SSB binding is completely blocked by full dsDNA monolayers of either A-Ac or B-Bc. The inability of SSB to bind to the dsDNA monolayers demonstrates that the surface hybridization efficiency of cDNA in solution to the ssDNA monolayers created by the pGlu attachment chemistry is essentially 100%.

D. SPR Imaging Measurements of Langmuir Isotherm of SSB Binding to ssDNA. As a final measurement of SSB

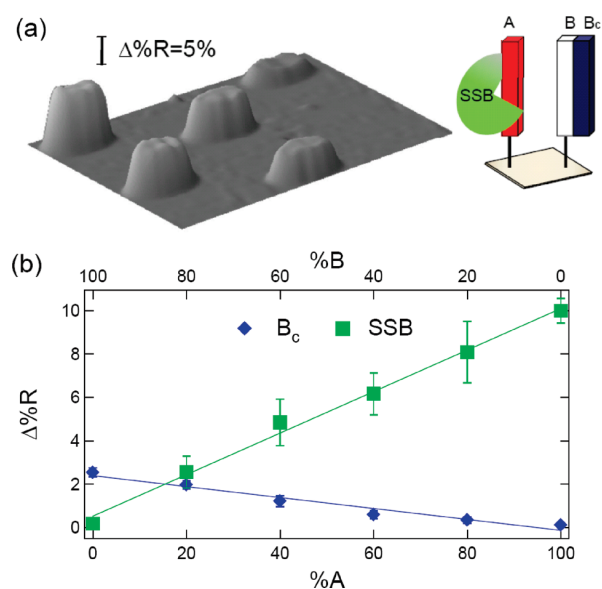


Figure 7. SPRI measurements of single-stranded binding protein (SSB) adsorption onto a partially hybridized ssDNA microarray containing mixtures of dsDNA (B-Bc) and ssDNA (A). The %A:%B ratios are the same as in Figure 4a. The microarray is first exposed to a 1 μ M solution of the complement Bc and then to a 10 nM solution of SSB. (a) SPR difference image of the microarray after SSB adsorption. (b) Quantitative plot of $\Delta\%R$ vs A:B percentage for the initial hybridization adsorption of Bc (diamonds) and the subsequent adsorption of SSB (squares).

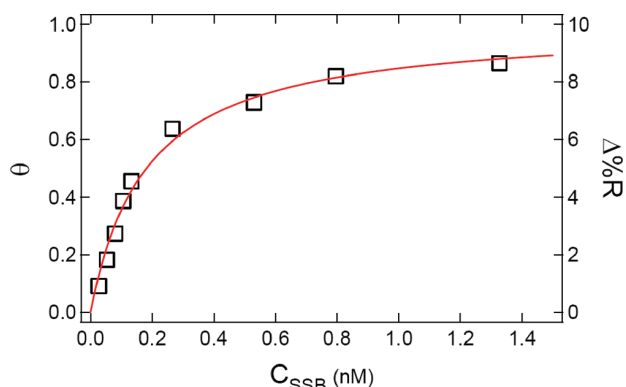


Figure 8. SPRI differential reflectivity measurements ($\Delta\%R$) of SSB binding to a ssDNA monolayer (sequence A) as a function of SSB concentration (C_{SSB}). $\Delta\%R$ values (squares) for concentrations ranging from 0.02 to 1.5 nM were measured after achieving equilibrium. The $\Delta\%R$ data was fit to a Langmuir adsorption isotherm (solid line) of relative surface coverage (θ) vs C_{SSB} . It was assumed that $\Delta\%R$ was proportional to θ . A Langmuir adsorption coefficient (K_{Ads}) of $(5.5 \pm 0.4) \times 10^9 \text{ M}^{-1}$ was obtained from the fit.

binding to the ssDNA monolayers, the adsorption of SSB was quantified using a series of equilibrium SPRI measurements at different SSB concentrations to obtain the adsorption isotherm. The $\Delta\%R$ obtained for adsorption to a 100% sequence A monolayer at various SSB concentrations is plotted in Figure 8. This data can be fit with a Langmuir isotherm³⁴ (the solid line in the figure) to obtain a Langmuir

(33) Revzin, A. *The Biology of Nonspecific DNA-Protein Interaction*; CRC Press: Boca Raton, FL, 1990.

(34) Adamson, A. W.; Gast, A. P. *Physical Chemistry of Surfaces*, 6th ed.; Wiley-Interscience: New York, 1997.

adsorption coefficient, K_{Ads} , of $(5.5 \pm 0.4) \times 10^9 \text{ M}^{-1}$, which is similar to the value of $1.7 \times 10^{10} \text{ M}^{-1}$ measured by Kozlov et al.³⁵ This large value of K_{Ads} confirms that in the mixed monolayer SSB binding experiments shown in Figures 6 and 7 all of the available ssDNA binding sites were occupied since the SSB solution concentration was 10 nM.

IV. Conclusions

The combination of PM-FTIR spectroscopy, SPR angle shift measurements, and SPR imaging measurements provides a powerful method for quantitating the chemical structure and bioavailability of ssDNA monolayers. Using these spectroscopic methods, we have demonstrated that the novel pGlu DNA surface attachment chemistry described and characterized in this paper leads to the fabrication of robust ssDNA microarrays that have very high surface hybridization efficiency, very little nonspecific adsorption, and can be used

in complex, multistep biosensing assays. One condition that these monolayers cannot survive is very high temperatures due to the cleavage of the MUAM gold–thiol bond. This problem can be alleviated by using this pGlu attachment chemistry on silicate or carbon modified gold surfaces.^{14,15} As observed in the SPRI measurements of SSB binding to the microarrays, these surfaces can also be used to quantitatively study the adsorption of proteins onto ssDNA and dsDNA monolayers. Future efforts will be directed toward the demonstration of surface enzyme reactions on these monolayers. This pGlu attachment chemistry may also be used to attach other amine-containing biomolecules (e.g., proteins, peptides) to gold films for biosensing applications.

Acknowledgment. This research was supported by the National Institute of Health (2RO1 GM059622-04 and 1R21 RR018475-01A2), the National Science Foundation (CHE-0551935), and the DARPA Micro/Nano Fluidics Fundamentals Focus MF3 Center at UCI. R.M.C. has a financial interest in GWC technologies.

(35) Kozlov, A. G.; Lohman, T. M. *Biochemistry* **2002**, *41*, 6032–6044.

(36) Georgiadis, R. M.; Peterlinz, K. P.; Peterson, A. W. *J. Am. Chem. Soc.* **2000**, *122*, 3166–3173.