

Characterizing the Incorporation of DNA into Single NIPAm Hydrogel Nanoparticles with Surface Plasmon Resonance Imaging Measurements

Brandon M. Matthews, Adam M. Maley, Kellen M. Kartub, and Robert M. Corn*

Department of Chemistry, University of California-Irvine, Irvine, CA 92697, USA.

Corresponding Author

*Robert M. Corn: rcorn@uci.edu

Abstract

N-isopropylacrylamide (NIPAm)-based hydrogel nanoparticles (HNPs) that incorporate 30mer single-stranded DNA (ssDNA) oligonucleotides were synthesized and characterized with single-nanoparticle surface plasmon resonance imaging (SPRI) microscopy, dynamic light scattering, transmission electron microscopy, and fluorescence measurements. The synthesized HNPs had an average diameter of 230 nm and exhibited a very large (5-10x) increase in the average single-nanoparticle SPRI refractive index ($\Delta\%R_{\text{NP}}$) as compared to HNPs without DNA. A combination of SPRI and fluorescence measurements was used to measure the uptake of approximately 20,000 complementary ssDNA into each HNP with a Langmuir isotherm adsorption coefficient of $4.89 \times 10^8 \text{ M}^{-1}$. The single-nanoparticle SPRI measurements also showed that only approximately 35% of the incorporated ssDNA was accessible for hybridization uptake and also for enzymatic hydrolysis using Exonuclease I. We attribute the presence of a large inactive ssDNA population in the nanoparticle to a combination of acrylamide Michael addition reactions to adenine, cytosine, and guanine nucleotides, as well as the possible formation of self-complementary secondary structures in the polymerized ssDNA.

Introduction

A variety of polymeric hydrogel nanoparticles (HNPs) are currently employed as nanoscale materials for the uptake, transport, collection and release of various therapeutics and biomarkers including drug molecules, peptides, proteins, nucleic acids, antibodies and even small metallic nanoparticles¹⁻¹⁰. For example, *N*-isopropylacrylamide (NIPAm)-based hydrogel nanoparticles that incorporate various ratios of tert-butyl and acrylic acid have been optimized for the specific uptake and delivery of the polypeptide melittin, the active component in honey bee venom¹¹, and the toxins in elapid snake venom¹². NIPAm-based HNPs have also been engineered to incorporate bioaffinity binding sites¹³, such as mannose sugars for the specific uptake of lectins¹⁴.

In this paper, we synthesize 230 nm NIPAm-based nanoparticles that incorporate single-stranded DNA (ssDNA) directly into the polymer, forming DNA-HNPs, and then quantitate their ssDNA binding affinity and exonuclease activity through a combination of single nanoparticle SPRI microscopy, fluorescence, dynamic light scattering (DLS), and transmission electron microscopy (TEM). The incorporation of ssDNA is an obvious choice as a versatile binding site due to its ability to hybridize to complementary nucleic acid sequences with excellent specificity¹⁵, to be hydrolyzed¹⁶ or ligated¹⁷ with various high efficiency DNA enzymes, and to fold into configurations that either bind molecular targets or exhibit enzymatic reactivity, releasing potential cargo¹⁸⁻²⁰. NIPAm-based hydrogels that incorporate and release ssDNA using these mechanisms have been used extensively in a thin film format, primarily on planar surfaces, but also in a core-shell nanoparticle format^{4, 21-23}. For example, DNA-HNPs were used in the uptake, delivery, and release small interfering RNA (siRNA) to infected cells^{9, 24-25}.

The DNA-HNP synthesis presented in Figure 1 incorporates a mixture of acrylamide-modified species in ratios similar to our previous work¹⁴, but with the addition of acrylic phosphoramidite-modified 30mer ssDNA. Acrylamide has demonstrated reactivity towards DNA, most notably via a Michael addition reaction to guanine, cytosine, and adenosine nucleotides²⁶⁻²⁷. These types of Michael addition reactions cause acrylamide to form DNA adducts, which have shown to be affect the biological activity of regulatory systems²⁸⁻³⁰. In the case of DNA-HNP formations, this interaction could give rise to additional polymerization sites, aiding in the incorporation of DNA as a whole³⁰. We theorize that this additional acrylamide cross-linking accounts for only observing approximately 35% of the incorporated ssDNA being available for hybridization with complementary ssDNA or enzymatic exonuclease activity.

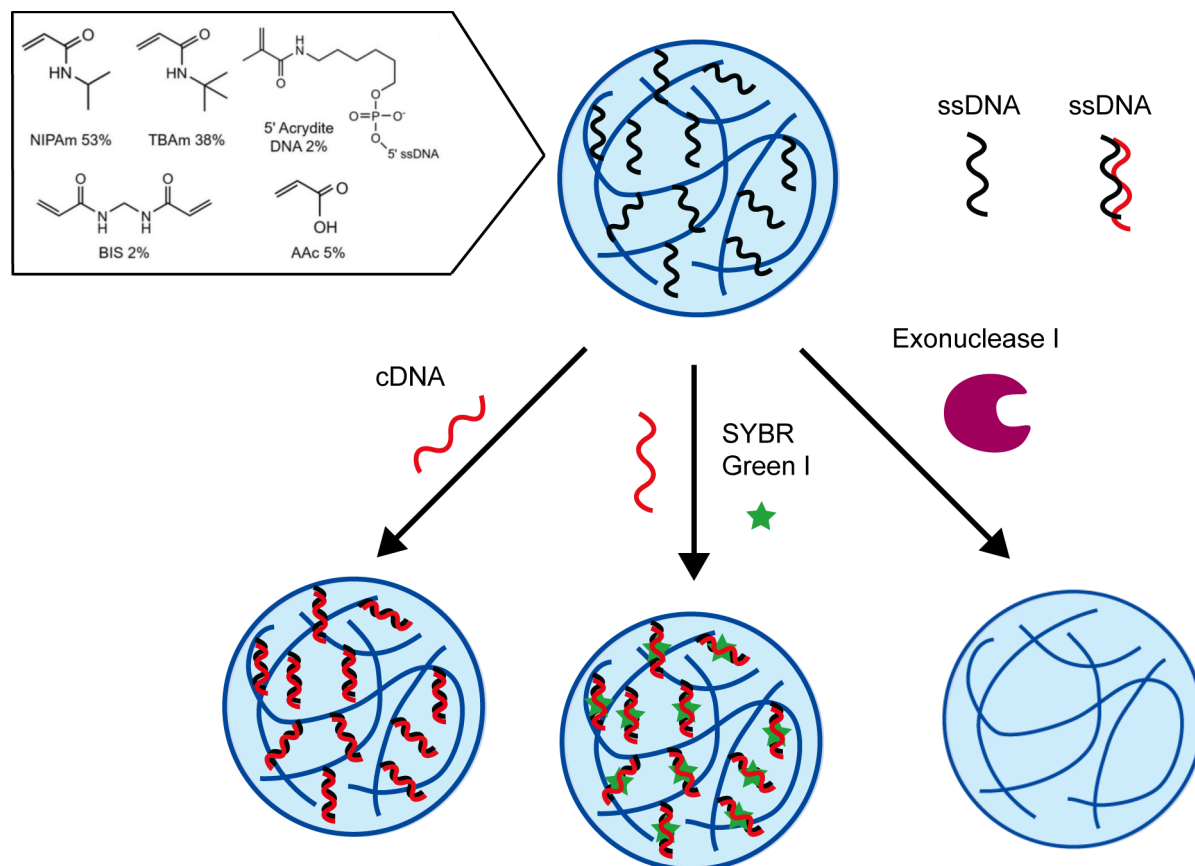


Figure 1. DNA-incorporated hydrogel nanoparticles (HNPs) were composed of *N*-isopropylacrylamide (NIPAm, 53 mol %), *N*-*tert*-butylacrylamide (TBAm, 38 mol %), acrylic acid (AAc, 5 mol %), *N,N*'-methylenebis(acrylamide) (BIS, 2 mol %), and 5'-modified acrylic phosphoramidite DNA (2 mol %). Following purification, incorporated DNA was tested to demonstrate accessibility and chemical activity, via specific complementary sequence hybridization to form dsDNA, fluorescent dyeing, and enzymatic activity through DNA hydrolysis.

Methods

Hydrogel Nanoparticle Materials. *N*-isopropylacrylamide (NIPAm), acrylic acid (AAc), sodium dodecyl sulfate (SDS), and ammonium persulfate (APS) were obtained from Sigma-Aldrich, Inc. (St. Louis, MO). *N,N*'-methylenebis(acrylamide) (BIS) was obtained from Fluka (St. Louis, MO). *N*-*tert*-butylacrylamide (TBAm) was obtained from Acros Organics (Geel,

Belgium). All DNA were purchased from Integrated DNA Technologies (Coralville, IA).

NIPAm was recrystallized from hexane before use. All other chemicals were used as received.

Hydrogel Nanoparticle Synthesis. HNP synthesis was adapted from the procedure detailed in *Cho, et. al*¹¹. The monomers NIPAm (53 mol %), TBAm (38 mol %), AAc (5 mol %), and BIS (2 mol %) were dissolved in 1.7 mL of nanopure water in a round-bottom flask for a total monomer concentration of 21 mM. TBAm was dissolved in 50 μ L of ethanol before addition to the monomer solution. The surfactant SDS (0.25 mg) was also added to the monomer solution to control nanoparticle size. Nitrogen gas was bubbled through the solution for 30 minutes. Following the addition of a 100 μ L aqueous solution containing 1 mg of APS, the polymerization reaction was carried out in an oil bath preset to 60 °C. After 30 minutes of reaction time, 1.3 μ mol (1 mM aqueous solution) of DNA was added to the reaction flask via syringe and the polymerization reaction was allowed to react for an additional 2.5 hours under nitrogen atmosphere. The resulting solution was purified by dialysis using a 12-14 kDa molecular weight cut off dialysis membrane against an excess amount of nanopure water (changed three times a day) for 3 days. Hydrogel nanoparticle size distribution and concentration were measured in aqueous solutions at 25 °C on a dynamic light scattering (DLS) instrument equipped with Zetasizer Software (Zetasizer Nano ZS, Malvern Instruments Ltd., Worcestershire, U.K.) and NanoSight NS300 Nanoparticle Tracking and Analysis microscopy system (Malvern Panalytical). Cryo-TEM images were obtained using 3 μ L of sample solution applied on a glow-discharged Quantifoil grid (Quantifoil, R2/2) and then loaded on Leica EMGP plunger (Leica Biosystem). The grid was quickly plunged into liquid propane after blotting away the excess liquid and the hydrogel particles were then embedded in a thin layer of vitrified ice on the grid. The cryo-grid was then transferred into a JEM-2100F electron microscope using a Gatan cryo-

transfer holder (Gatan, Inc). The electron microscope was operated at 200KV with a field emission gun and specimen was examined under minimum dose system. The images were recorded on a OneView camera (Gatan, Inc) at 40,000X magnification, corresponding to 0.28nm per pixel at specimen space.

Substrate Preparation. The Au substrates were coated by thermal vapor deposition of a 1 nm Cr adhesion layer and 45 nm Au onto borosilicate No. 1.5 coverslips (Fisherbrand, Pittsburgh, PA). The Au surface was immobilized with 1-undecanethiol (C11) by immersing the Au substrate into a 1 mM C11/EtOH solution. The Au surface was partitioned using adhesive silicon isolation wells (Electron Microscopy Sciences, Hatfield, PA).

SPRI Microscopy Measurements. The SPRI microscope setup is described in a previous publication³¹. The microscope was built into the frame of an IX51 inverted microscope (Olympus, Tokyo, Japan). A 1 mW, 814 nm diode laser (Melles Griot, Carlsbad, CA) was expanded and collimated using a spatial filter (Newport Corp., Newport Beach, CA). The beam was polarized and focused with a lens ($f=200$ mm) and then directed onto the back focal plane of a 100 \times 1.49 high numerical aperture objective (Olympus). The beam was directed upward near the edge of the objective by a gold-coated knife-edge mirror (Thorlabs, Newton, NJ). The reflected image was passed out the other side of the objective and acquired by an Andor Neo sCMOS camera (South Windsor, CT). Each three-second reflectivity image was acquired by accumulating 30 11-bit, 0.1 s exposures.

Enzymatic SPRI Measurements. Exonuclease I (5 μ L of 20 U/ μ L; New England Biolabs) was added to 1 to 10 diluted 10x reaction buffer (67 mM Glycine-KOH, 6.7 mM MgCl₂, 10 mM β -ME, pH 9.5) and a 1 to 10 stock diluted D1-HNP solution to a final volume of 500 μ L in nanopure water. The solution was incubated at 37 °C for 1 h before undergoing three wash

cycles similar to the fluorescence measurements described above. After the final wash, the solution was then resuspended to a final volume of 50 μ L.

Results and Discussion

A. Synthesis and Characterization of DNA-HNPs

Four types of DNA-HNPs were synthesized and then characterized via a combination of DLS, TEM imaging, fluorescence measurements and single-nanoparticle surface plasmon resonance imaging (SPRI) microscopy. DNA-HNP size distribution was obtained by DLS and confirmed using TEM imaging. Through the combination of fluorescence loss measurements and nanoparticle tracking measurements, an incorporated DNA concentration of approximately $22,000 \pm 1,000$ fluorophores per nanoparticle was found.

The primary DNA sequence used for DNA-HNPs analysis is denoted as D1; its complementary sequence is labeled D1c, and control sequence D1nc. To analyze potential influences of the nucleotides used during synthesis, three additional sequences were also used: a modified 30mer sequence from *Lilienthal, et. al.*¹⁸, a poly-T sequence, and a poly-A sequence, denoted as D2, D3, and D4 respectively. All sequence used are summarized in Table 1. A large amount of D1 ssDNA was found incorporated into the HNPs, suggesting some degree of cooperativity between the ssDNA and the acrylamide polymerization process. SPRI nanoparticle measurements showed that the resultant DNA-HNPs were able to specifically hybridize complementary 30mer ssDNA (D1c) with nanomolar binding efficiency and were easily hydrolyzed by the DNA enzyme Exonuclease I.

Table 1. ssDNA sequences incorporated into various batches of DNA-HNPs

Label	DNA sequence
D1	5'-Acrydite- TCT GTG ATT AGC GAT TGT TTA GGT GTA TGC-3'

D1c	5'-GCA TAC ACC TAA ACA ATC GCT AAT CAC AGA-3'
D1nc	5'-CGA AAT CCA GAC ACA TAA GCA CGA ACC GAA-3'
D2	5'-Acrydite- TTT TTT TTT TTT TTT TTT TCT TCA TTG TTT-3'
D3	5'-Acrydite-TTT TTT TTT TTT TTT TTT TTT TTT TTT TTT-3'
D4	5'-Acrydite-AAA AAA AAA AAA AAA AAA AAA AAA AAA AAA-3'

The primary method used to characterize the activity of the DNA-HNPs was near infrared single-nanoparticle SPRI microscopy. This relatively new microscopic single-nanoparticle method has been employed recently to detect and characterize distributions of polymeric, oxide, and metal nanoparticles based on the nanoparticle's integrated refractive index³²⁻³⁵. In a single-nanoparticle SPRI measurement, a total internal reflection microscope geometry is used with an 814 nm laser to excite traveling wave surface plasmon polaritons (SPPs) onto a 45 nm gold thin film attached to a microscope slide cover. Upon exposure to an aqueous solution of nanoparticles, SPRI reflectivity images (100 μm x 100 μm) are obtained every three seconds from this microscope for ten minutes. These images are subtracted sequentially from each other to create a set of 200 SPRI differential reflectivity ($\Delta\%R$) images.

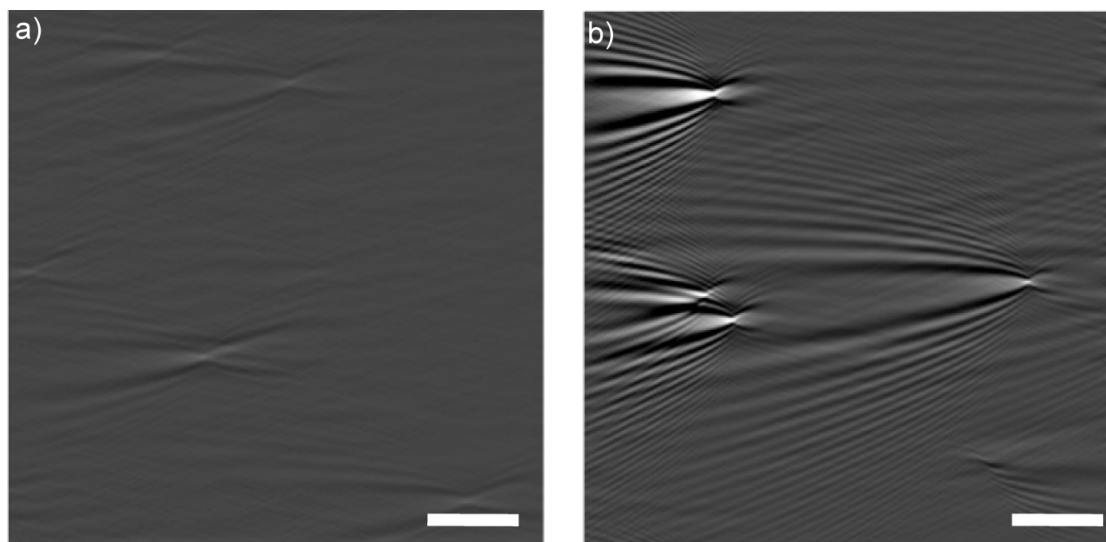


Figure 2. Example SPRI differential reflectivity images of (a) HNPs and (b) DNA-HNPs, irreversibly adsorbing to the gold thin-film surface. The scale bar for both images is 10 μm .

An example of one of these three second SPRI differential reflectivity images obtained during the exposure of a gold thin film to a solution of DNA-HNPs is shown in Figure 2. The gold has been modified with a 1-undecanethiol monolayer to create a hydrophobic surface onto which the DNA-HNPs irreversibly adsorb through hydrophobic forces. Each irreversible nanoparticle binding event on the gold surface in the three-second time window creates a distinctive point diffraction pattern in the image due to the interaction of the nanoparticle refractive index with the traveling SPPs. The shape and intensity of these diffraction patterns have been modeled and quantitated previously³¹⁻³²; the intensity of each DNA-HNP binding event can be quantitated to obtain a single-nanoparticle reflectivity change value, $\Delta\%R_{\text{NP}}$. We have shown in previous papers that $\Delta\%R_{\text{NP}}$ depends on both the size and composition of the adsorbed nanoparticle. As such, $\Delta\%R_{\text{NP}}$ can be thought of as the “integrated refractive index” of the adsorbed nanoparticle. A collection of 300 - 400 $\Delta\%R_{\text{NP}}$ values for synthesized DNA-HNPs were obtained over several experiments, and results summarized in Table 2 along with DLS size distribution measurements.

Table 2. Hydrodynamic Size Measurements from DLS for Hydrogel Nanoparticles and Statistics from Single-Nanoparticle SPRI measurements for Hydrogel Nanoparticles

Nanoparticle	Diameter (nm)	$\langle\Delta\%R_{\text{NP}}\rangle$	Standard Deviation (s)	95% CI	# of NPs
D0-HNP	246 ± 3	0.51	0.16	0.02	357
D1-HNP	234 ± 5	5.18	2.04	0.22	320

D2-HNP	202 ± 2	2.38	1.17	0.11	424
D3-HNP	216 ± 1	0.59	0.32	0.32	304
D4-HNP	196 ± 3	2.11	0.98	0.10	403
D1-HNP + Exonuclease I	-	3.16	2.09	0.31	180

Figure 3 plots two data sets of $\Delta\%R_{NP}$ values obtained from two different groups experiments, one for the adsorption of HNPs without DNA incorporation (D0) and one for the adsorption of D1-HNPs, both as a functions of time. The two types of HNPs have significantly different average $\Delta\%R_{NP}$ values (which we denote as $\langle\Delta\%R_{NP}\rangle$) of $0.51 \pm 0.02\%$ for D0-HNPs and $5.18 \pm 0.22\%$ for D1-HNPs, with ranges represented as 95% confidence intervals. The addition of acrylamide-modified ssDNA to the NIPAm polymerization has led to an almost tenfold increase in $\langle\Delta\%R_{NP}\rangle$. In contrast, DLS measurements on the two types of nanoparticles show only a slight change in nanoparticle diameter from 246 ± 3 nm to 234 ± 5 nm, for D0-HNPs and D1-HNPs respectively. Cryo-TEM images of D1-HNPs were collected also to show the particles are not aggregating together and to further corroborate their sizes, demonstrated in Figure 4.

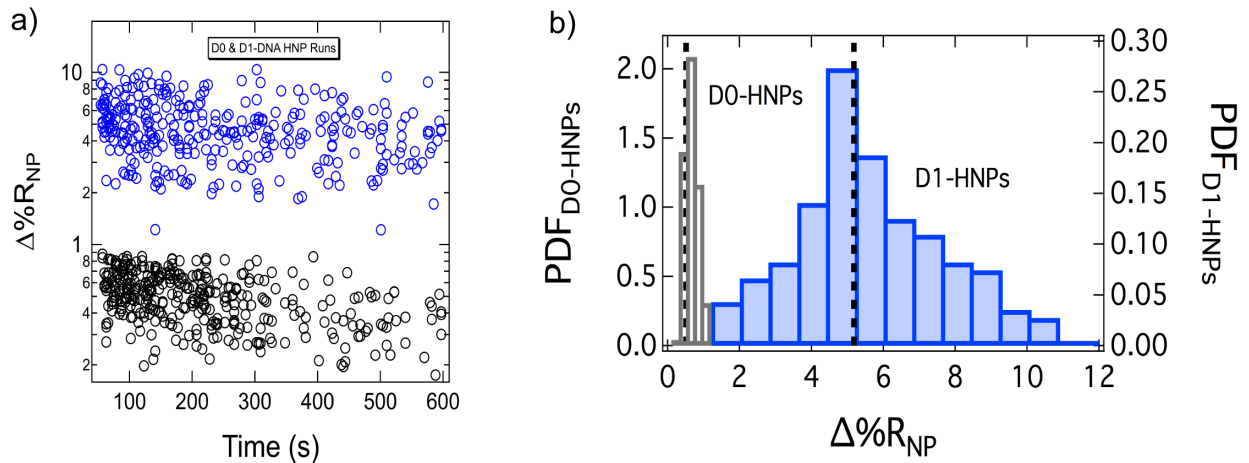


Figure 3. (a) Time-dependent distribution of $\Delta\%R_{NP}$ values of HNPs with (blue) and without (black) DNA incorporation, measured in separate experiments. Each circle represents the $\Delta\%R_{NP}$ for a single HNP irreversibly adsorbing to the chemically modified surface. (b) $\Delta\%R_{NP}$ frequency distribution histograms obtained from the SPRI adsorption measurements of HNPs (transparent gray bars) and DNA-HNPs (blue bars). The averages for each distribution are denoted by the dotted black lines within each distribution. Average $\Delta\%R_{NP}$ for HNPs and DNA-HNPs are $0.51 \pm 0.02\%$ and $5.18 \pm 0.22\%$, respectively.

The large increase in $\langle \Delta\%R_{NP} \rangle$ when comparing D0-HNPs to D1-HNPs is due to an increase in both nanoparticle density and refractive index in the presence of acrylamide-modified ssDNA (Figure 3). This large increase strongly suggests that (i) a significant amount of 30mer ssDNA has been incorporated into the D1-HNP, and (ii) the presence of the acrylamide-modified ssDNA during polymerization has altered the structure of the hydrogel in a manner that has increased its density. Surprisingly, the increase in $\langle \Delta\%R_{NP} \rangle$ is significantly less when the 30mer sequence is altered to contain more thymine nucleotides: for D2-HNPs which have over half of the 30mer nucleotide sequence replaced by thymine, the signal drops to $2.38 \pm 0.11\%$, and for D3-HNPs which incorporate a poly-T ssDNA 30mer, the signal drops to all the way down to $0.59 \pm 0.03\%$, just slightly larger than the D0-HNPs. These additional measurements strongly suggest that the large increase in $\langle \Delta\%R_{NP} \rangle$ for the DNA-HNPs can be attributed to previously observed Michael addition reactions of the acrylamide with adenine, cytosine, and guanine nucleotides during the polymerization process^{27, 29, 36}. Thymine nucleotides do not react with acrylamide at physiological pH, and thus there is no incorporation of the poly-T ssDNA 30mers into the D3 HNPs²⁷. This is further corroborated by the observed incorporation of poly-A ssDNA 30mers into the D4 HNPs, where the signal once again increases since adenine is capable

of undergoing a Michael addition reaction. The reaction of acrylamide with A, C and G in the ssDNA greatly assist in the overall incorporation of ssDNA into the nanoparticle and also provide additional crosslinking of the ssDNA and hydrogel. A second potential mechanism for sequence dependent ssDNA incorporation would be the formation of self-complementary secondary structures between ssDNA that lead to greater packing and thus denser incorporation of ssDNA into the HNPs. These interactions are typically much weaker, and DNA folding calculations are shown to have a free energy of $-0.98 \text{ kcal/mol}^{37}$, proving that the D1 sequence do not show a large degree of folding or secondary structure.

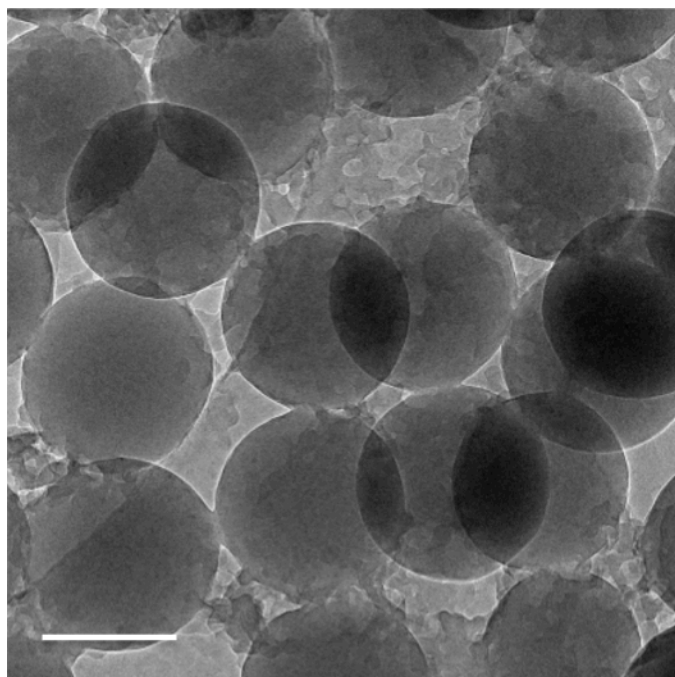


Figure 4. Cryo-TEM image of vitrified D1-HNPs. Scale bar is 200 nm.

B. Hybridization Uptake of Complementary ssDNA by DNA-HNPs

To determine the ability of the DNA-HNPs to uptake and hybridize complementary ssDNA from solution, we employed a combination of fluorescence and single-nanoparticle SPRI measurements. Using D1-HNPs, fluorescence loss measurements were performed using fluorescently labeled complementary DNA (D1c) to estimate the loading capacity of DNA into

the HNPs. On average, approximately 20,000 fluorophore-modified ssDNA were incorporated into the DNA-HNPs, corresponding to 35% of the total accessible incorporated DNA within the nanoparticles. Further details are given in the Supplemental Information.

To verify that the incorporation of complementary D1c into the D1-HNPs was due to hybridization to form dsDNA, fluorescence measurements using the intercalation of SYBR Green I into dsDNA were performed to demonstrate duplex formation in the DNA-HNPs. The fluorescence spectrum of DNA-HNPs with either complementary (solid blue line) or non-complementary (dotted black line) ssDNA, both at a 10 nM solution, is shown in Figure 5. SYBR Green I preferentially stains dsDNA formations and, as seen in Figure 5, a strong fluorescence signal was only observed in the presence of complementary ssDNA. These results demonstrate that the uptake of complementary ssDNA into the DNA-HNPs is driven by duplex formation to create dsDNA.

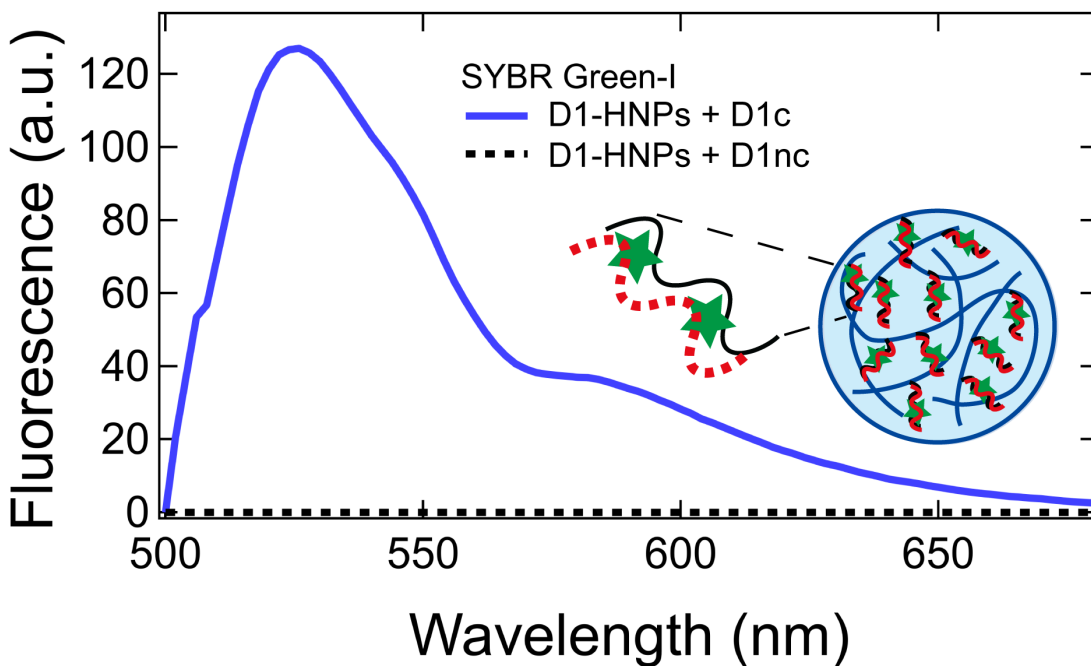


Figure 5. Fluorescence spectra of D1-HNPs in the presence of SYBR Green-I dye and either complementary (D1c) or non-complementary (D1nc) ssDNA. D1-HNPs were mixed initially

with either of the ssDNA, followed by fluorescent dye. Parallel measurements were then performed after three centrifuge/wash cycles before D1-HNPs mixtures were re-suspended in buffer solution. The solid blue curve indicated the formation of dsDNA within D1-HNPs with its complementary sequence, D1c, and SYBR Green staining. No fluorescence was observed in the D1nc mixture (dotted black line), as SYBR Green preferentially stains dsDNA formations.

Single-nanoparticle SPRI measurements were used to quantitate the hybridization uptake of complementary ssDNA into the D1-HNPs. Figure 6 shows the change in the $\Delta\%R_{NP}$ distribution of the DNA-HNPs after exposure to a 100 nM complementary ssDNA solution. The average $\langle\Delta\%R_{NP}\rangle$ increased by approximately 2% (from $5.18 \pm 0.22\%$ to $7.11 \pm 0.25\%$). As a control experiment, negligible change in $\langle\Delta\%R_{NP}\rangle$ was observed for DNA-HNPs in the presence of 100 nM non-complementary ssDNA. These SPRI measurements confirm the ability of these HNPs to incorporate target ssDNA by sequence-specific hybridization.

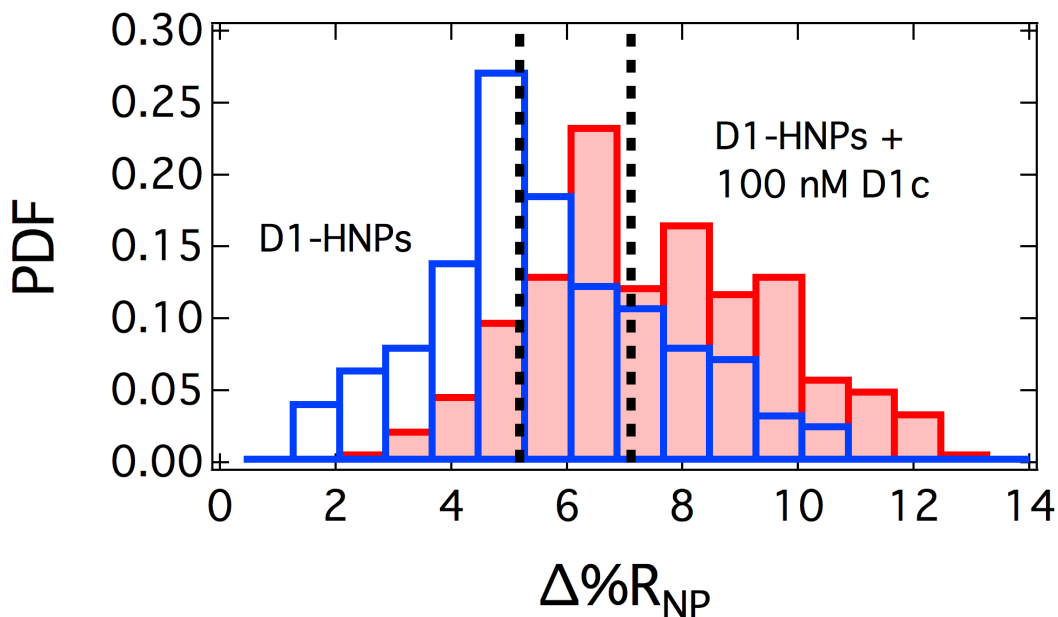


Figure 6. $\Delta\%R_{NP}$ frequency distribution histograms obtained from the SPRI adsorption measurements of D1-HNPs onto Au surfaces. The transparent blue bars indicate D1-HNPs

before exposure to its complementary sequence, D1c. When exposed to D1c, D1-HNPs uptake the ssDNA, causing a shift in $\Delta\%R_{NP}$ signal, shown as solid red bars. The dotted black lines for each distribution denote the averages, $5.18 \pm 0.22\%$ and $7.11 \pm 0.25\%$ for D1-HNPs and D1-HNPs in the presence of D1c, respectively.

SPRI measurements were performed to determine the concentration dependence of the hybridization uptake of complementary ssDNA into the DNA-HNPs. The change in the average $\langle \Delta\%R_{NP} \rangle$ for the DNA-HNPs is plotted versus the log of complementary ssDNA concentration in Figure 7. The solid red line in the figure is a fit of this concentration dependence to a Langmuir adsorption isotherm. The Langmuir adsorption coefficient for this fit is $4.89 \times 10^8 \text{ M}^{-1}$; the inverse of this number, about 2 nM, is the concentration for which half of the adsorption sites are filled. The value for the Langmuir adsorption coefficient is approximately 5-10 times higher than that observed for the adsorption of complementary ssDNA to ssDNA monolayers on gold thin films³¹; this result suggests that duplex formation is more favorable in the DNA-HNPs as compared to on a surface, most likely due to the increased flexibility and access of the ssDNA in the three dimensional hydrogel format.

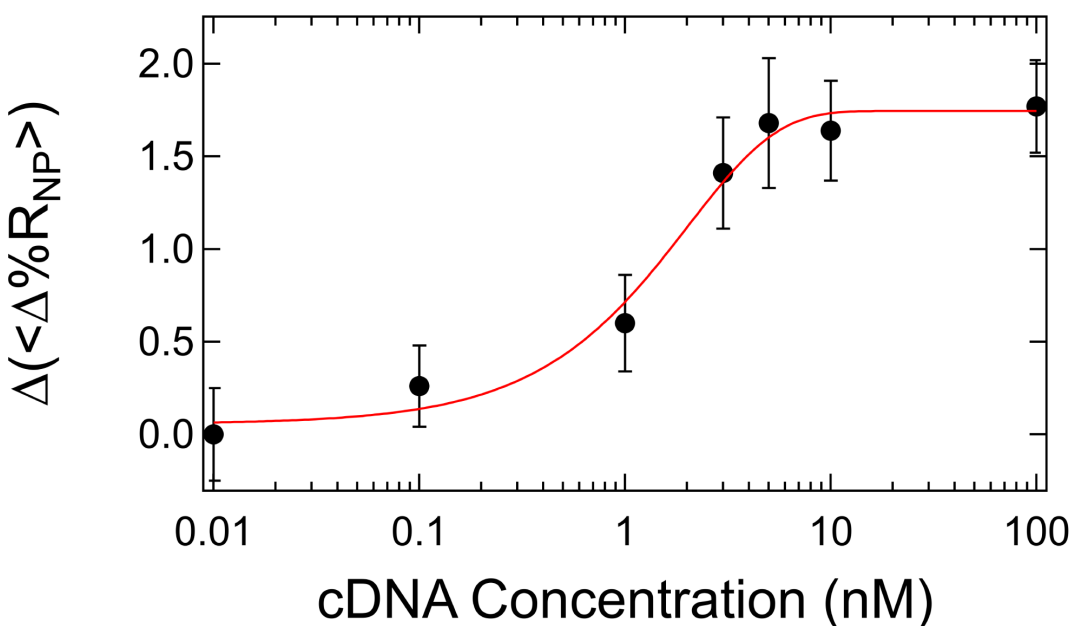


Figure 7. Langmuir isotherm fit of the change in $\langle \Delta \% R_{NP} \rangle$, comparing unoccupied D1-HNPs to D1-HNPs loaded with D1c. Each measurement is the difference between the $\Delta \% R_{NP}$ signal concentration at a D1c concentration and empty D1-HNPs. The adsorption constant K_{Ads} was determined to be $4.89 \times 10^8 \text{ M}^{-1}$.

C. Enzymatic Hydrolysis of ssDNA in DNA-HNPs.

As a demonstration of the bioavailability of the ssDNA in the HNPs, SPRI measurements were used to monitor the enzymatic hydrolysis of the ssDNA in the nanoparticles. The DNA enzyme Exonuclease I will exclusively hydrolyze ssDNA, but not dsDNA. SPRI nanoparticle measurements were performed on DNA-HNPs after exposure to a solution of Exo I for 1 hour; Figure 8 plots $\Delta \% R_{NP}$ distributions pre- (blue bars) and post-exposure (green bars) of Exo I. A significant decrease in $\langle \Delta \% R_{NP} \rangle$ was observed, dropping the value from 5.18% to $3.16 \pm 0.31\%$ after enzymatic activity; we attribute this decrease to the hydrolysis of ssDNA in the DNA-HNP. Interestingly, this decrease in $\langle \Delta \% R_{NP} \rangle$ is approximately the same value as the maximum

amount of increase in $\langle \Delta\%R_{NP} \rangle$ observed in hybridization adsorption experiments in Figure 7, maintaining roughly the same percentage of accessibility as DNA duplex formation.

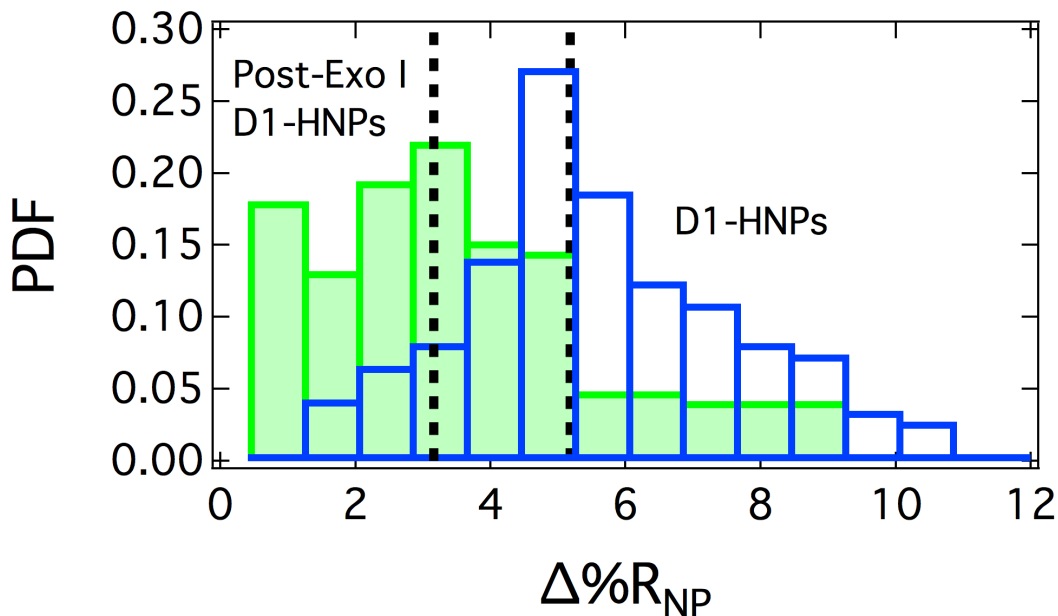


Figure 8. Single-nanoparticle SPRI frequency distributions comparing DNA-HNPs distributions before (transparent blue bars) and after (solid green bars) exposure to Exonuclease I. The dotted lines for each distribution represent the $\Delta\%R_{NP}$ averages for pre- and post-exposure, $5.18 \pm 0.22\%$ and $3.16 \pm 0.31\%$, respectively.

Conclusions and Future Directions

In conclusion, we have shown in this paper that DNA-HNPs can be prepared via the incorporation of acrylamide-modified 30mer ssDNA and that they can be used to uptake complementary ssDNA by hybridization adsorption/incorporation. Moreover, the ssDNA in the DNA-HNPs can undergo enzymatic hydrolysis, demonstrating the availability of the incorporated ssDNA to enzymatic activity. An almost tenfold increase is observed in average $\langle \Delta\%R_{NP} \rangle$ for the D1-HNPs as compared to HNPs without ssDNA; this large increase is attributed to both the inclusion of acrylamide-modified ssDNA into the hydrogel and its effect on

the polymerization process. Specifically, the Michael addition of acrylamide to A, C, and G nucleotides in the ssDNA assisted in the incorporation of DNA into the DNA-HNPs. However, this reaction limited the bioavailability of the ssDNA within DNA-HNPs to about 35%. Future work will focus on the further synthesis, nucleic acid/protein uptake and enzymatic activity of various ssDNA sequences, such as aptamers, in these DNA-HNPs.

Supporting Information

SYBR Green I fluorescence measurements, fluorescence loss measurements and statistical data for SPRI adsorption measurements.

Notes

The authors declare no competing financial interests.

Acknowledgments

This work was supported by the National Science Foundation through grant CHE-1807317. DLS and nanoparticle size distribution and concentration data were acquired at the Laser Spectroscopy Facility in the Department of Chemistry at UC, Irvine. We would also like to thank Christian Baca for his assistance in data acquisition and analysis, and Dr. Li Xing for her help in acquiring cryo-TEM images. Cryo-TEM work was performed at the UC Irvine Materials Research Institute (IMRI).

References

1. Zhang, Z.; Liu, J. Intracellular delivery of a molecularly imprinted peroxidase mimicking DNAzyme for selective oxidation. *Mater. Horiz.* **2018**, 5 (4), 738-744.

2. Huang, Y.; Ma, Y.; Chen, Y.; Wu, X.; Fang, L.; Zhu, Z.; Yang, C. J. Target-responsive DNAzyme cross-linked hydrogel for visual quantitative detection of lead. *Anal. Chem.* **2014**, *86* (22), 11434-11439.
3. Karimi, M.; Ghasemi, A.; Sahandi Zangabad, P.; Rahighi, R.; Moosavi Basri, S. M.; Mirshekari, H.; Amiri, M.; Shafaei Pishabad, Z.; Aslani, A.; Bozorgomid, M.; Ghosh, D.; Beyzavi, A.; Vaseghi, A.; Aref, A. R.; Haghani, L.; Bahrami, S.; Hamblin, M. R. Smart micro/nanoparticles in stimulus-responsive drug/gene delivery systems. *Chem. Soc. Rev.* **2016**, *45* (5), 1457-1501.
4. Kahn, J. S.; Hu, Y.; Willner, I. Stimuli-Responsive DNA-Based Hydrogels: From Basic Principles to Applications. *Acc. Chem. Res.* **2017**, *50* (4), 680-690.
5. Peppas, N. A.; Hilt, J. Z.; Khademhosseini, A.; Langer, R. Hydrogels in Biology and Medicine: From Molecular Principles to Bionanotechnology. *Adv. Mater.* **2006**, *18* (11), 1345-1360.
6. Carvalho, W. S. P.; Wei, M.; Ikpo, N.; Gao, Y.; Serpe, M. J., Polymer-Based Technologies for Sensing Applications. *Anal. Chem.* **2018**, *90* (1), 459-479.
7. Hamidi, M.; Azadi, A.; Rafiei, P. Hydrogel nanoparticles in drug delivery. *Adv. Drug Deliv. Rev.* **2008**, *60* (15), 1638-1649.
8. Vermonden, T.; Censi, R.; Hennink, W. E. Hydrogels for protein delivery. *Chem. Rev.* **2012**, *112* (5), 2853-2888.

9. Segovia, N.; Pont, M.; Oliva, N.; Ramos, V.; Borros, S.; Artzi, N. Hydrogel doped with nanoparticles for local sustained release of siRNA in breast cancer. *Adv. Healthcare Mater.* **2015**, *4* (2), 271-280.
10. Plamper, F. A.; Richtering, W. Functional Microgels and Microgel Systems. *Acc. Chem. Res.* **2017**, *50* (2), 131-140.
11. Cho, K.; Fasoli, J. B.; Yoshimatsu, K.; Shea, K. J.; Corn, R. M. Measuring Melittin Uptake into Hydrogel Nanoparticles with Near-Infrared Single Nanoparticle Surface Plasmon Resonance Microscopy. *Anal. Chem.* **2015**, *87* (9), 4973-4979.
12. O'Brien, J.; Lee, S.-H.; Gutiérrez, J. M.; Shea, K. J. Engineered nanoparticles bind elapid snake venom toxins and inhibit venom-induced dermonecrosis. *PLOS Neglected Trop. Dis.* **2018**, *12* (10), e0006736.
13. Miura, Y.; Hoshino, Y.; Seto, H. Glycopolymer Nanobiotechnology. *Chem. Rev.* **2016**, *116* (4), 1673-92.
14. Maley, A. M.; Terada, Y.; Onogi, S.; Shea, K. J.; Miura, Y.; Corn, R. M. Measuring Protein Binding to Individual Hydrogel Nanoparticles with Single-Nanoparticle Surface Plasmon Resonance Imaging Microscopy. *J. Phys. Chem. C* **2016**, *120* (30), 16843-16849.

15. Chen, Y.; Nakamoto, K.; Niwa, O.; Corn, R. M. On-chip synthesis of RNA aptamer microarrays for multiplexed protein biosensing with SPR imaging measurements. *Langmuir* **2012**, *28* (22), 8281-8285.
16. Freeman, R.; Liu, X. Q.; Willner, I. Amplified Multiplexed Analysis of DNA by the Exonuclease III-Catalyzed Regeneration of the Target DNA in the Presence of Functionalized Semiconductor Quantum Dots. *Nano. Lett.* **2011**, *11* (10), 4456-4461.
17. Frutos, A. G.; Smith, L. M.; Corn, R. M. Enzymatic ligation reactions of DNA "words" on surfaces for DNA computing. *J. Am. Chem. Soc.* **1998**, *120* (40), 10277-10282.
18. Lilienthal, S.; Shpilt, Z.; Wang, F.; Orbach, R.; Willner, I. Programmed DNzyme-Triggered Dissolution of DNA-Based Hydrogels: Means for Controlled Release of Biocatalysts and for the Activation of Enzyme Cascades. *ACS Appl. Mater. Interfaces* **2015**, *7* (16), 8923-8931.
19. Song, S.; Wang, L.; Li, J.; Fan, C.; Zhao, J., Aptamer-based biosensors. *TrAC, Trends Anal. Chem.* **2008**, *27* (2), 108-117.
20. Breaker, R. R.; Joyce, G. F. A DNA enzyme with Mg²⁺-dependent RNA phosphoesterase activity. *Chem. Biol.* **1995**, *2* (10), 655-660.

21. Moura, L. M.; Martinho, J. M. G.; Farinha, J. P. S. DNA Hybridization in Thermoresponsive Polymer Nanoparticles. *ChemPhysChem* **2010**, *11* (8), 1749-1756.
22. Fujita, M.; Hiramane, H.; Pan, P.; Hikima, T.; Maeda, M. Effects of Complementary DNA and Salt on the Thermoresponsiveness of Poly(N-isopropylacrylamide)-b-DNA. *Langmuir* **2016**, *32* (4), 1148-1154.
23. Soontornworajit, B.; Zhou, J.; Shaw, M. T.; Fan, T. H.; Wang, Y. Hydrogel functionalization with DNA aptamers for sustained PDGF-BB release. *Chem. Commun. (Cambridge, U. K.)* **2010**, *46* (11), 1857-1859.
24. Smith, M. H.; Lyon, L. A. Multifunctional nanogels for siRNA delivery. *Acc. Chem. Res.* **2012**, *45* (7), 985-993.
25. Dunn, S. S.; Tian, S.; Blake, S.; Wang, J.; Galloway, A. L.; Murphy, A.; Pohlhaus, P. D.; Rolland, J. P.; Napier, M. E.; DeSimone, J. M. Reductively responsive siRNA-conjugated hydrogel nanoparticles for gene silencing. *J. Am. Chem. Soc.* **2012**, *134* (17), 7423-7430.
26. Zeynep Atay, N.; Çalgan, D.; Özakat, E.; Varnali, T. Acrylamide and glycidamide adducts of Guanine. *J. Mol. Struct.: THEOCHEM* **2005**, *728* (1), 249-251.
27. Besaratinia, A.; Pfeifer, G. P. DNA adduction and mutagenic properties of acrylamide. *Mutat. Res. Genet. Toxicol. Environ. Mutagen.* **2005**, *580* (1), 31-40.

28. Watzek, N.; Böhm, N.; Feld, J.; Scherbl, D.; Berger, F.; Merz, K. H.; Lampen, A.; Reemtsma, T.; Tannenbaum, S. R.; Skipper, P. L.; Baum, M.; Richling, E.; Eisenbrand, G. N7-Glycidamide-Guanine DNA Adduct Formation by Orally Ingested Acrylamide in Rats: A Dose–Response Study Encompassing Human Diet-Related Exposure Levels. *Chem. Res. Toxicol.* **2012**, *25* (2), 381-390.
29. Huang, S.; Lu, S.; Huang, C.; Sheng, J.; Zhang, L.; Su, W.; Xiao, Q., An electrochemical biosensor based on single-stranded DNA modified gold electrode for acrylamide determination. *Sens. Actuators, B* **2016**, *224* (C), 22-30.
30. Freeman, R.; Han, M.; Álvarez, Z.; Lewis, J. A.; Wester, J. R.; Stephanopoulos, N.; McClendon, M. T.; Lynsky, C.; Godbe, J. M.; Sangji, H.; Luijten, E.; Stupp, S. I. Reversible self-assembly of superstructured networks. *Science* **2018**, *362* (6416), 808-813.
31. Halpern, A. R.; Wood, J. B.; Wang, Y.; Corn, R. M. Single-nanoparticle near-infrared surface plasmon resonance microscopy for real-time measurements of DNA hybridization adsorption. *ACS Nano* **2014**, *8* (1), 1022-1030.
32. Maley, A. M.; Lu, G. J.; Shapiro, M. G.; Corn, R. M. Characterizing Single Polymeric and Protein Nanoparticles with Surface Plasmon Resonance Imaging Measurements. *ACS Nano* **2017**, *11* (7), 7447-7456.

33. Zybin, A.; Kuritsyn, Y. A.; Gurevich, E. L.; Temchura, V. V.; Uberla, K.; Niemax, K. Real-time Detection of Single Immobilized Nanoparticles by Surface Plasmon Resonance Imaging. *Plasmonics* **2010**, *5* (1), 31-35.
34. Wang, W.; Tao, N. Detection, counting, and imaging of single nanoparticles. *Anal. Chem.* **2014**, *86* (1), 2-14.
35. Yu, H.; Shan, X.; Wang, S.; Tao, N. Achieving High Spatial Resolution Surface Plasmon Resonance Microscopy with Image Reconstruction. *Anal. Chem.* **2017**, *89* (5), 2704-2707.
36. Solomon, J. J.; Fedyk, J.; Mukai, F.; Segal, A. Direct Alkylation of 2'-Deoxynucleosides and DNA following *in Vitro* Reaction with Acrylamide. *Cancer Res.* **1985**, *45*, 3465-3470.
37. Gruber, A. R.; Lorenz, R.; Bernhart, S. H.; Neuböck, R.; Hofacker, I. L. The Vienna RNA websuite. *Nucleic Acids Res.* **2008**, *36* (Web Server issue), W70-W74.

TOC Image

